



Scholars Research Library

Der Pharma Chemica, 2011, 3 (4):102-109
(<http://derpharmachemica.com/archive.html>)



ISSN 0975-413X
CODEN (USA): PCHHAX

Synthesis, characterization and ion-exchanging properties of novel oligomeric azo dyes

¹J. R. Patel, ²K. S. Nimavat and ³K. B. Vyas

¹M. B. Patel Sci. College, Anand, Gujarat,

²Govt. Sci. College, Gandhinagar, Gujarat

³Sheth L. H. Sci. College, Mansa, Gujarat

ABSTRACT


The oligomeric azo dye based on 3-amino-phenol-Formaldehyde (APF) polymer was prepared by diazotization of Aniline and coupling with 3-amino-phenol-Formaldehyde (AP) resin. The AAPF was then treated with 5-chloromethyl-8-hydroxyquinoline hydrochloride in the presence of a THF in conc. NaOH (PH 9-10) at room temperature for 7 hrs. The resultant oligomeric ligand designated as azopolyphenol-Formaldehyde-5-chloromethyl-8-hydroxyquinoline (AAPF-HQ) was characterized by elemental analysis, IR spectral studies, and thermogravimetry. The polymeric metal chelates of AAPF-HQ with Cu^{2+} , Zn^{2+} , Mn^{2+} , Ni^{2+} , UO_2^{2+} and Co^{2+} metal ions were prepared and characterised by metal:ligand ratio, IR and reflectance studies, magnetic properties, thermogravimetry and microbicidal activity. The AAPF-HQ sample was also monitored for its chelating and ion-exchanging properties. Batch equilibration method has been adopted, for evaluation of ion-exchange properties.

Keywords: 3-amino-phenol-Formaldehyde (APF) polymer, 5-chloromethyl-8-hydroxyquinoline, polymeric metal Chelates, IR spectra, ion-exchange properties, Batch equilibrium method, thermogravimetry.

INTRODUCTION

The effluents from mines and metal industries set up the serious problems in removal of heavy toxic metal ions. The contents of these metals in effluent are almost above the valid limit. The ion-exchange resin are of organic polymera and play a pivotal role in various commodity application [1-3]. The ion-exchange resin can be use for metal extraction from ore, analytical reagent, and separation of metal ion and deionization of water [4-10]. Most of commercial ion-exchange resins are sulfonated polystyrene-divinylbenzene copolymer [11-12]. The use of complex ion-formation in ion-exchange resin has been prepared to solve the problem [11-12]. The phenol-formaldehyde type resin have also been reported as ion-exchange resin [13]. One of the resin 3-amino-phenol-Formaldehyde is reported for the purposes but its modification into

oligomeric ligand has not been reported. Thus, the aim of the present work to prepare and study the novel ion-exchange resin based on 3-aminophenol. The present paper comprises the studies on novel ion-exchange resin containing a well known metal complexing agent and 8-hydroxyquinoline. The synthetic route is shown below.

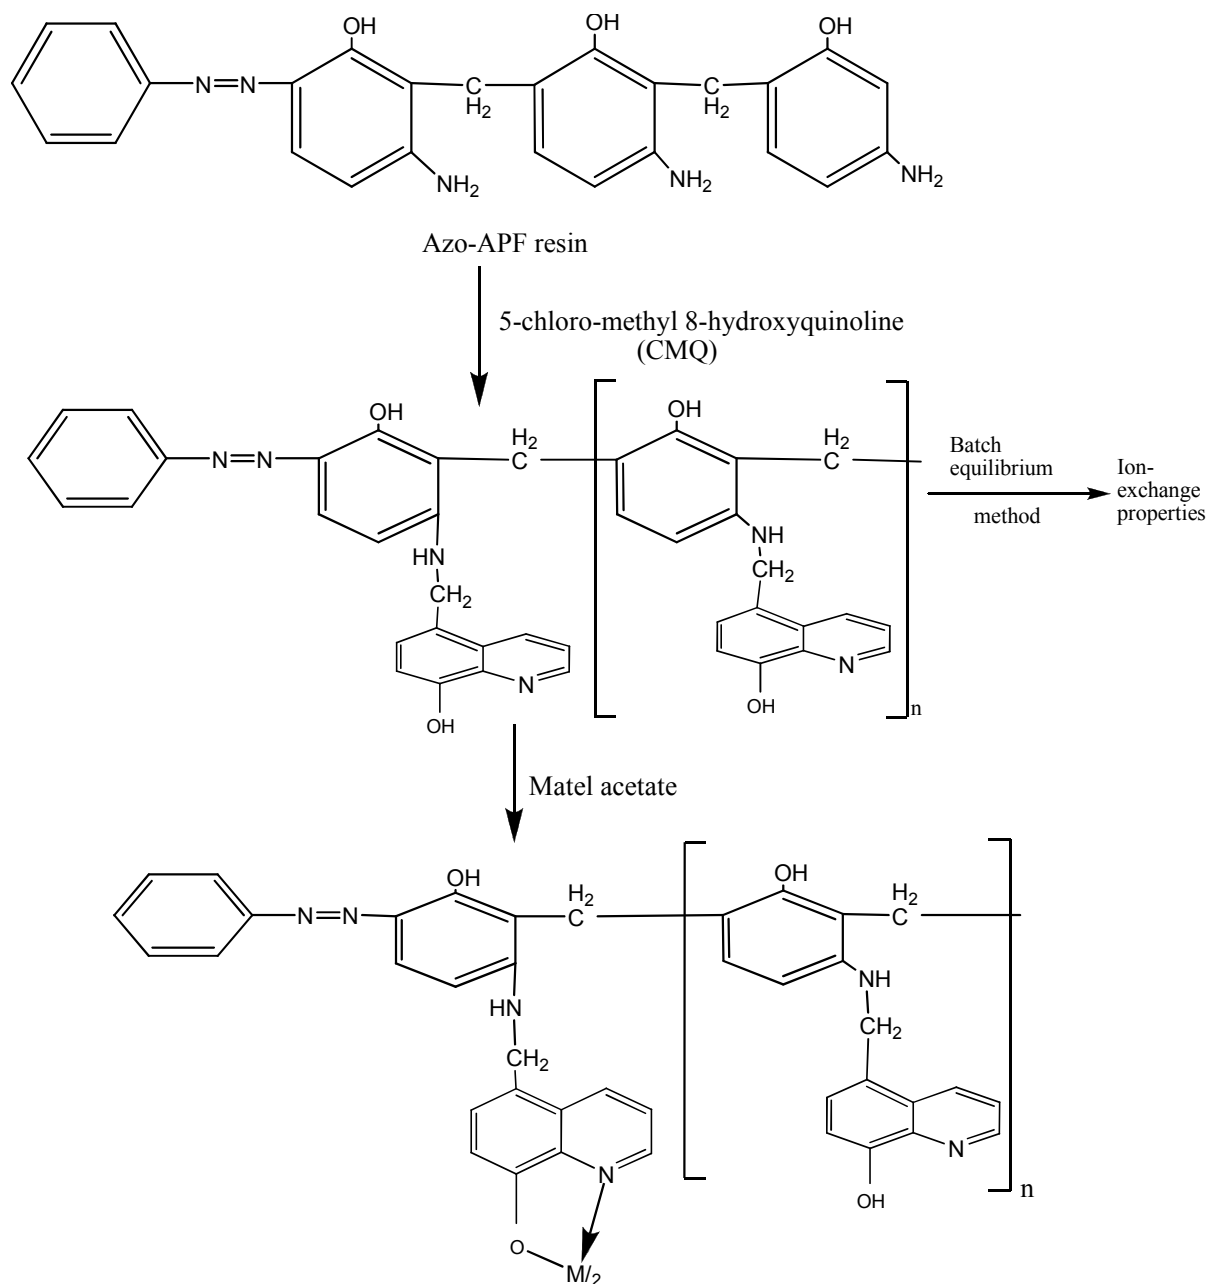

MATERIALS AND METHODS

Experimental

Materials: All the chemicals used were of either pure or analytical grade.

Synthesis of 3-amino-phenol-Formaldehyde (APF) polymer were prepared by method reported in literature [13]. The 5-chloromethyl-8-hydroxyquinoline hydrochloride (m.p. 280°C) was prepared by method reported in literature [14].

Synthesis of azo dyes based on 3-amino phenol-formadehyde (AAPF)

Preparation of azo coupling of aryl diazonium salts to phenol-formadehyde (APF):

Phenyldiazonium salt solution (0.1mole) was slowly added to an alkaline solution of 3-amino-Phenol-Formaldehyde polymer (APF) (0.1mole) at pH 8.5-9.0 and below 0-5°C. The resultant solution was stirred for 2hr. The dye was precipitated by lowering the pH to 6.0. The precipitated dye (AAPF) was filtered off, wash with water and air-dried. The yield of APF was 69% and m.p. 162-164°C (uncorrected). The predicted structure and formation of oligomeric ligand is shown in Scheme-1.

Synthesis of azo-3-amino phenol-Formaldehyde-5-chloromethyl-8-hydroxyquinoline (AAPF-HQ)

To a mixture of AAPF oligomeric (0.01 mole) and 5-chloromethyl-8-hydroxyquinoline (0.01 mole) in THF (100 ml), Conc. NaOH was added with maintaining pH 9-10 of the mixture was heated upto 60°C gently for 5 minute and it was stirred at room temperature for 7 hrs. The resulted gel type material was filtered, washed by water and air-dried. It was powdered to 100 mesh size. Yield was 82%. It did not melt up to 300°C and insoluble in water and common organic solvents.

Synthesis of oligomeric chelates:

The polymeric metal chelates of AAPF-HQ were synthesized by reaction of AAPF-HQ with corresponding metal acetates. The detail procedure is as follow.

A dried AAPF-HQ oligomer (0.01 mole) was dispersed in 200 ml aqueous solution of 20% aqueous formic acid and warmed on a water bath for 10 minutes. To this dispersed solution a warm solution of metal acetate (0.01 mole) in 50% aqueous formic acid solution was added drop wise with constant stirring. The reaction mixture as made alkaline with dilute ammonia solution in order to coagulate oligomeric chelates. The resultant contents were further digested on water bath for an hour. Finally the solid polymer chelates were filtered off Washed with hot water followed by acetone, DMF and dried in air. The polymer chelates of AAPF-HQ with Cu^{2+} , Co^{2+} , Ni^{2+} , Mn^{2+} , UO_2^{2+} and Zn^{2+} transition metal ions.

Measurements

Elemental analyses for C,H and N content were carried out on TF 1101 elemental analyzer (Italy). IR spectra of oligomer ligand and their metal chelates were scanned on a NICOLET 760 DR FTIR spectrophotometer in KBr phase. The metal content of polychelates was performed by decomposing a weighed amount of each polymer chelate followed by EDTA titration as reported in literature [15].

Magnetic susceptibility measurements of all the polychelates were carried out at room temperature by the Gouy method using Mercury tetrathiocyanato cobaltate (II) $\text{Hg}[\text{Co}(\text{NCS})_4]$ as a calibrant. The diffuse reflectance spectra of all the solid polychelates were recorded on a Backman DK-2A spectrophotometer with solid reflectance attachments. MgO was employed as the reference attachments. MgO was employed as the reference compound. Thermal behaviour of these metal chelates was studied by TGA perfomed on thermogravimetric analyzer.

The batch equilibration method was adopted for the ion-exchanging properties [16-17]. The evaluation of the influence of different electrolytes on metal uptake by the polymer, the rate of metal uptake under specified conditions and distribution of various metal ions of different PH values were carried out following the details of the procedures described earlier[16-17].

RESULTS AND DISCUSSION

The oligomer sample AAPF-HQ was in form of dark brown powder and insoluble in common organic solvents. It swells up to some extent in conc. NaOH solution. It did not melt up to 300°C. The elemental contents shown in Table-1 are consistent with the predicted structure. The IR spectrum of AAPF-HQ shows a broad band extending from 3400-3100 cm^{-1} with maxima at 3400, 3330 cm^{-1} attributed to -OH group and NH_2 group. The weak bands at 2932 cm^{-1} and 2850 cm^{-1} are attributed to asymmetric and symmetric stretching vibrations of methylene groups (- CH_2 -). The bands around at 1420, 1480, 1588, and 1600 cm^{-1} are due to 8-hydroxyquinoline moiety [18]. These features confirm the proposed structure of ligand AAPF-HQ. The TGA of AAPF-HQ contains single step degradation. The degradation starts from 280°C, loss rapidly between 300 to 500 and almost lost 85% at 650°C.

Characterization of Polymeric Chelates:

The polymeric chelates of AAPF-HQ with different metal ions such as Cu^{2+} , Ni^{2+} , Co^{2+} , Mn^{2+} , UO_2^{2+} and Zn^{2+} vary in color from dark green to brown. They generally resemble each other. Comparison of IR spectra of the parent ligand with their polymer chelates has revealed certain characteristics differences as mentioned below.

One of the significant differences to be expected between IR spectrum of parent ligand and its metal chelates is the present at sharp 3400 cm^{-1} due to Sec. NH stretching vibration frequencies in IR spectrum of polymer chelates. However the band due to absence of as the oxygen O-H of parent ligand has not been predicated due to presence of already OH group of resin. However this band has explicable by the fact that water molecules might have strongly absorbed to the chelates during the formation.

Another noticeable difference is that the bands due to C=N stretching vibration of 8-quinolionol at 1606 cm^{-1} in IR spectrum of AAPF-HQ has assigned to implane O-H deformation and this is shifted towards higher frequency in the spectra of polymer chelates indication the formation of metal-oxygen bonds [19-21]. This has been further confirmed by a weak band at 1100 cm^{-1} . Corresponding to C-O-M stretching frequency [19-21]. All these characteristic features of IR suggest the general structure of polymer chelates as shown in Scheme I.

Examination of data about metal content in each polymer chelates (Table- I and II) has revealed a 1:1 metal:ligand stoichiometry in all the polychelates. Magnetic moment (μ_{eff}) data of polymer chelates given in Table I has reveals that all metal chelates like Cu^{2+} , Ni^{2+} and Co^{2+} are paramagnetic, while that of Zn^{2+} is diamagnetic in nature. The electronic spectral data assignments are shown in Table-3. The electronic spectra of AAPF-HQ with Cu^{+2} ions show two broad bands at 14952 and 23530 cm^{-1} due to ${}^2\text{T}_{1g} \rightarrow {}^2\text{E}_g$ transition and charge transfer spectra respectively suggesting a distorted octahedral structure for AAPF-HQ polymer chelates. The AAPF-HQ with Ni^{2+} and Co^{+2} ion polychelates give two absorption bands respectively at 14926, 24097 cm^{-1} and 14926, 22472 cm^{-1} corresponding to ${}^4\text{T}_g \rightarrow {}^2\text{T}_{1g}$, ${}^4\text{T}_{1g} \rightarrow {}^4\text{T}_{1g}(\text{P})$ transition. Thus, absorption band of diffuse reflectance spectral and the values of magnetic moment (μ_{eff}) have indicated an octahedral configuration for the Ni^{2+} , and Co^{2+} polychelates. The spectra of polychelates of Mn^{2+} ion show two weak bands at 17242 cm^{-1} and 25032 cm^{-1} assigned to the

transition ${}^6A_{1g} \rightarrow {}^4T_{2g}$ (4G) and ${}^6T_{1g} \rightarrow {}^4T_{1g}$ (4G) respectively and assigned an octahedral structure for AAPF-HQ chelates. As the spectrum of the Zn^{2+} chelates is not well resolved it is not interpreted but its μ_{eff} value reveals its diamagnetic nature as expected. The TGA data (TG thermograms not shown) of all polymeric chelates are shown in Table-2. The TGA data as thermograms reveals that the rate of decomposition of all polymeric chelates is initially low up to 200°C temperature and rapidly increases to maximum in the range 400-500 °C. This might be due to accelerated catalytically by `insitu` formation of metal oxide of thermal stability of all these polychelates is quite similar.

Ion-Exchange properties

The examination of data presented in Table-2 reveals that the amount of metal ions taken up by a given amount of the AAPF-HQ polymer depends upon the nature and concentration of the electrolyte present in the solution. The amounts of Fe^{3+} , Cu^{2+} and UO_2^{2+} ions taken up by the polymer sample increase with the increase in concentration of ions taken up by the polymer sample increase with the increase in concentration of ions like chloride, chlorate and nitrate but decrease with the increase in concentration of the sulfate ions. The amounts of the remaining three metal ions Co^{2+} , Mn^{2+} , and Zn^{2+} , taken by the polymer sample decrease with the increase in concentration of chlorate, chloride, nitrate and sulfate ions.

Rate of metal uptake

The rates of metal absorption by the AAPF-HQ sample were measured for Fe^{3+} , UO_2^{2+} , Cu^{2+} and Mn^{2+} ions presence of 1 M $NaHCO_3$ to know the time required to reach the stage of equilibrium. All experiments were carried out at pH 3. The examination of the results presented in Table.3 shows that UO_2^{2+} and Fe^{3+} ions required slightly more than three hours for the establishment of equilibrium and Cu^{2+} and Mn^{2+} ions required about five hrs for the purpose. In the experiments with solution containing UO_2^{2+} and Fe^{3+} ions, more than 70% of equilibrium was established in the first hrs. This reveals that the rate of uptake of metal ions follows the order UO_2^{2+} , $Fe^{3+} > Cu^{2+} > Mn^{2+}$. The rates of uptake of Zn^{2+} and Co^{2+} ions have been found to be very low at pH 3. Hence the values are no reported.

Table-1 Elemental analyses of polymeric metal Chelates of AAPF-HQ and their metal chelates

Sample designation	Elemental Analysis					Elemental Analysis					
	N%		M%		μ_{eff}	%Weight loss at different temperature °C					
	Cald	Found	Cald	Found	B.M	200	300	400	500	600	700
AAPF-HQ	11.96	11.9	-----	----	-----	200	300	400	500	600	700
AAPF-HQ (Cu^{2+})	11.58	11.5	3.28	3.2	1.78	8.9	12	28	50	65	81
AAPF-HQ (Ni^{2+})	11.61	11.5	3.04	3.0	3.00	7.8	17.6	22.8	54	68	90
AAPF-HQ (UO_2^{2+})	10.46	10.4	12.61	12.6	D	8.4	16.8	27.6	56.4	73	89.5
AAPF-HQ (CO_2^{2+})	11.61	11.6	3.05	3.0	4.03	8.5	19.8	22.4	62.2	70.1	92
AAPF-HQ (Mn^{2+})	11.63	11.6	2.85	2.8	4.68	8.6	14.7	23.4	60.1	72	93
AAPF-HQ (Fe^{3+})	11.63	11.6	2.90	2.8	4.93	8.7	15.3	24.6	63.1	73	96
AAPF-HQ (Zn^{2+})	11.57	11.5	3.37	3.3	D	8.2	17.9	26.8	54.9	63	90

OH groups: 2 per repeat unit.
 IR features: 3600-2200 cm^{-1} (-OH-)
 1604, 1500, 3050 cm^{-1} (aromatic),
 2930, 2850, 1430 cm^{-1} (-CH₂-)

Distribution ratio of metal ions at different pH values

The results described in Table.4 reveal that the amount of metal ions taken up by the polymer sample AAPF-HQ at equilibrium increases with the increase in pH. The selectivity of the polymer sample UO_2^{2+} and Fe^{3+} ions are higher than that for each of the remaining metal ions. The distribution ratio for Fe^{3+} ions is lower than that for UO_2^{2+} by about 1800 units at pH 3. The lower values of the distribution ratio for Fe^{3+} ions requires its attachment with proper sites on three different polymer chains and that of the UO_2^{2+} ion requires such an attachment with sites on two polymer chains. Among the remaining metal ions, Cu^{2+} has a high value of distribution ratio at pH 6 while the other three metal ions Co^{2+} , Zn^{2+} , and Mn^{2+} have a low distribution ratio over a pH range from 4 to 6. Further work in the direction of wide range at such polymers and their ion exchanging properties are under progress.

Table-2 Evaluation of the influence of different electrolytes in the uptake of several metal ions; ($[\text{Mt}(\text{NO}_3)_2] = 0.1 \text{ mole} \cdot \text{l}^{-1}$)^a

Metal ions	PH	[Electrolyte] ($\text{mole} \cdot \text{l}^{-1}$)	Adsorption of $\text{mmol} \cdot 10^1$ of the metal ion on AAPF-HQ polymer ^b .			
			NaClO_4	NaNO_3	NaCl	Na_2SO_4
Cu^{2+}	5.5	0.01	0.09	0.07	0.13	0.27
		0.05	0.19	0.10	0.15	0.26
		0.1	0.13	0.16	0.18	0.25
		0.5	0.28	0.18	0.20	0.23
		1.0	0.45	0.23	0.26	0.21
Fe^{3+}	2.75	0.01	0.08	0.12	0.05	0.17
		0.05	0.23	0.16	0.06	0.07
		0.1	0.25	0.14	0.09	0.09
		1.0	0.33	0.24	0.26	0.06
UO_2^{2+}	4.0	0.01	0.17	0.16	0.13	0.20
		0.05	0.21	0.19	0.16	0.22
		0.1	0.16	0.25	0.18	0.24
		0.5	0.24	0.46	0.23	0.21
		1.0	0.54	0.43	0.25	0.18
Co^{2+}	5.5	0.01	0.13	0.14	0.06	0.06
		0.05	0.12	0.15	0.12	0.09
		0.1	0.06	0.14	0.08	0.07
		0.5	0.05	0.08	0.06	0.05
		1.0	0.02	0.03	0.05	0.03
Mn^{2+}	5.5	0.01	0.22	0.25	0.20	0.15
		0.05	0.19	0.22	0.18	0.12
		0.1	0.16	0.19	0.21	0.06
		0.5	0.13	0.19	0.17	0.07
		1.0	0.15	0.18	0.14	0.04
Zn^{2+}	5.5	0.01	0.13	0.09	0.09	0.13
		0.05	0.15	0.07	0.07	0.06
		0.1	0.11	0.06	0.04	0.09
		0.5	0.07	0.05	0.06	0.05
		1.0	0.06	0.03	0.03	0.03
Ni^{2+}	5.5	0.01	0.08	0.11	0.08	0.16
		0.1	0.19	0.14	0.06	0.07
		0.5	0.18	0.17	0.07	0.08
		1.0	0.30	0.21	0.21	0.04

a. Volume of electrolyte solution 40 ml, time 24h, volume of metal ion solution 1ml, temp. 25 °C

b. Wt. of PATS polymer 25 mg.

Table-3 Comparison of the rates of metal (Mt) ion uptake ^a

Time (h)	Attainment of equilibrium state ^b			
	Fe ³⁺	UO ₂ ²⁺	Cu ²⁺	Mn ²⁺
0.5	62.3	31.2	34.8	21.9
1	71.4	66.3	51.4	46.4
2	88.6	84.7	63.3	62.8
3	91.2	91.3	74.4	76.2
4	90.3	95.9	83.7	83.9
5	---	---	89.3	85.7
6	---	---	93.9	91.8
7	---	---	93.2	97.3

a. $[Mt(NO_3)_2] = 0.1 \text{ mole} \cdot l^{-1}$, volume 1 ml, $[NaNO_3] = 1 \text{ mol} \cdot l^{-1}$, volume 40 ml, pH = 3, temp 25° C, wt of PATS polymer 25 mg.

b. Related to the amount of metal ions taken up at the state of equilibrium assumed to be established in 24 h and assumed to be 100%.

Table-4 Distribution ratios, D, of different metal ions as a function of the Ph

pH	Distribution ratio ^a of metal ions ^b					
	Cu ²⁺	Fe ³⁺	UO ₂ ²⁺	Co ²⁺	Mn ²⁺	Zn ²⁺
1.5	-----	-----	249	----	-----	-----
1.75	124	126	425	----	-----	-----
2.0	160	165	514	---	----	----
2.5	446	448	543	---	----	----
3.0	945	947	2786	----	----	----
4.0	---	---	----	3	74	77
5.0	----	----	----	77	136	136
6.0	---	---	----	335	257	257

^a mmol of metal ions taken up by 1 g of polymer

mmol of ions present in 1 ml of solution

$[Mt(NO_3)_2] = 0.1 \text{ mol } l^{-1}$, volume: 1 ml; wt. of polymer: 25 mg ; $[NaNO_3] = 1 \text{ mol } l^{-1}$, volume: 44 ml; temp.: 25 °C, time 24 h (equilibrium state).

^b Error +/- 5%.

REFERENCES

- [1] Wing, R.E., Doane, W.in. and Runell, C.R. , *J.Appl. Polym. Sci* 19, 847 (1995)
- [2] Metra, A.K.D, and Karchadhanvi, A. *IInd. J. Chem.* 39 B, 311 (2000)
- [3] Martin, L.F. Industrial water Purification Noyes Data corporation Park Ridge New Jercey, (1974)
- [4] Bento, L.S.M., *Proc. Sugar process. Res. Conf.* 1990, 99-115 (1991).
- [5] U.S.Pat. 5,084, 285 (Jan. 28, 1992), Shimatani, M. and co.Workeres (to snow brand milk products co., Ltd.).
- [6] Sprockel, O.L., and Price, J.C., *Drug Dev. Ind. Pharm.* (16 (2), 361-376 (1990).
- [7] U.S.Pat. 4,978,807, (Dec. 18, 1990), Smith ,L.A., (to chemical research & Licensing Co.)
- [8] Ahmed, F.E., Young, B.D., and Bryson, A.W., *Hydrometallurgy* 30 (1-3), 257-275 (1992)
- [9] Ritter, J.A., and Bibler, J.P., *water Sci. Techno.* 25(3), 165-172 (1992).
- [10] CEP, C.R., 70-77 (Aug.1979)
- [11] U.S.Pat 2,366,007 (Dec.26, 1945), G.F.D' Alelio (to General Electric co.)
- [12] U.S.Pat. 2,596, 417 (Apr.22,1952), G.F.D' Alelio (to General Electric co.)
- [13] Vyas, M.V.; Kapadia, R. N. ,;*Indian J. Technol.*, 19, 491- 49(1981).
- [14] Burckhalter, J. H. and Leib, R. I., *J. Org. Chem.*, 26, 4078 (1961).

- [15] Vogel.A. I.(1978) *Textbook of Quantitative Chemical Analysis*, (ELBS 4th Edn. London). pp 317 Co. Bombay,(1972).
- [16] Greger, H.P., Tieter, M., Citaval L., and Becker E.I. *Ind. Eln. Chem.* 44,2834(1952).
- [17] Decoeso, R.C., Donarma, L.G. and Tanic, E.A, *Anal. Chem.* 34, 845(1962).
- [18] Charles, R. G. Freiser, H. F. Priedel, R. Hilliand,L. E. Johnston, R. D., *Spectrochem. Acta.* 8, 1 (1956).
- [19] Narayan. S., Bhave,S.B. and Kharat, R.B., *J. Indian Chem, Soc.*, 58,1194(1981).
- [20] Agrawal. D.R. and Tandon,S.G., *J. Indian Chem. Soc.*, 48,6(1971).
- [21] Gandhi. N.R and Munshi, K.N, *J. Indian, Chem Soc.*, 59,1290(1982).